

Review

Collagen Biosynthesis to Engineered Biomaterials: Molecular Design, Synthetic Strategy, and Biomedical Application

Xinzhi Zhou ^{1,2}, Zhaocheng Weng ², Chen Zhao ^{1,2}, Qiang Zhang ^{2,3,*}, Xuye Lang ^{1,2}, Baiyi Lu ^{2,4,*} and Yuan Yao ^{1,2,*}

¹ College of Chemical and Biological Engineering, Zhejiang University, Hangzhou 310027, China; zhouxinzhi@zju.edu.cn (X.Z.); 22428134@zju.edu.cn (C.Z.); xuyelang@zju.edu.cn (X.L.)

² Zhejiang Synthetic Biomanufacturing Innovation Center, Zhejiang Key Laboratory of Intelligent Manufacturing for Functional Chemicals, ZJU-Hangzhou Global Scientific and Technological Innovation Center, Zhejiang University, Hangzhou 311200, China; wzcwill@163.com (Z.W.)

³ Zhejiang University-University of Illinois Urbana-Champaign Institute, Zhejiang University, Haining 314400, China

⁴ College of Biosystems Engineering and Food Science, Key Laboratory for Quality Evaluation and Health Benefit of Agro-Products of Ministry of Agriculture and Rural Affairs, Key Laboratory for Quality and Safety Risk Assessment of Agro-Products Storage and Preservation of Ministry of Agriculture and Rural Affairs, Zhejiang University, Hangzhou 310027, China

* Corresponding author. E-mail: qiangzhang@intl.zju.edu.cn (Q.Z.); bylu@zju.edu.cn (B.L.); yyao1@zju.edu.cn (Y.Y.)

Received: 12 February 2025; Revised: 3 March 2025; Accepted: 20 August 2025; Available online: 4 September 2025

ABSTRACT: Collagen, a principal component of the extracellular matrix, provides mechanical strength and stability to tissues and organs through its structural organization. Its biocompatibility has established it as a crucial material in biomedical applications such as drug delivery systems, cell culture matrices, and tissue engineering scaffolds. However, the use of animal-derived collagen carries risks of pathogen transmission, which has driven research towards developing synthetic collagen alternatives. Advances in AI-assisted protein engineering are accelerating the design of synthetic collagens and their applications in biomaterials. This review examines collagen's structural characteristics, biosynthesis strategies, biological activities as well as AI-assisting engineering.

Keywords: Collagen; Extracellular matrix; Biomaterial; AI-assisting engineering; Synthetic biology



© 2025 The authors. This is an open access article under the Creative Commons Attribution 4.0 International License (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Collagen, a principal component of the extracellular matrix (ECM) [1], constitutes ~30% of the human body's total protein content. It represents 70% of the skin's dry weight, and ~90% of the protein in tendons and corneal tissue [2]. The collagen family comprises 28 types, with molecular isomerism underpinning functional and structural diversity (Table 1) [3]. This heterogeneity governs collagen's physicochemical characteristics. Some types of collagen have a triple-helix structural feature (Figure 1). These chains intertwine into a superhelix (Figure 1). The repeating (Gly-X-Y)_n motif facilitates tight packing of the helices, where X and Y are frequently proline and hydroxyproline. Hydrogen bonds form between the carbonyl group of the X-position residue in one chain and the amide nitrogen of glycine in an adjacent chain [4], creating a lattice parallel to the polypeptide backbone and perpendicular to the helical axis [5].

Table 1. The diversity of the collagen family.

Collagen Type Extraction Difficulty		Function	Category	Collagen Subtypes
Collagen I	No	Provide tensile strength [6]	Fibrillar collagen	Banded fibrils
Collagen II	No	Provide compressive strength and elasticity [7]	Fibrillar collagen	Banded fibrils
Collagen III	No	Provides support in soft tissues and maintains elasticity [8]	Fibrillar collagen	Banded fibrils
Collagen IV	Strong ECM interactions	Provide scaffolding for epithelial and endothelial layers [9]	Non-fibrillar collagen	Network-forming collagens
Collagen V	Strong ECM interactions, abundant in the embryonic stage	Co-assemble with type I collagen in tissues like skin and placenta [10]	Fibrillar collagen	Banded fibrils
Collagen VI	Low abundance, strong ECM interaction	Mechanical support, cytoprotective function, promotion of tumor growth and progression [11]	Non-fibrillar collagen	Beaded microfibrils
Collagen VII	Low abundance, strong ECM interaction	Provide stability to the dermal-epidermal adhesion [12]	Non-fibrillar collagen	Anchoring fibrils
Collagen VIII	Low abundance, strong ECM interaction	Active roles in angiogenesis and ECM remodeling [13]	Non-fibrillar collagen	Short chain collagens
Collagen IX	Low abundance, strong ECM interaction	Support cartilage integrity and stability [14]	Non-fibrillar collagen	FACIT
Collagen X	Low abundance, strong ECM interaction	Regulate matrix mineralization and compartmentalizing matrix components [15]	Non-fibrillar collagen	Fibril-associated collagens
Collagen XI	Abundant in embryonic stage, strong ECM	Regulate collagen fibrillogenesis [16]	Fibrillar collagen	Fibril-forming collagens
Collagen XII	Low abundance, strong ECM interaction	Stabilize type I collagen fibrils [17]	Non-fibrillar collagen	FACIT
Collagen XIII	Transmembrane nature	Function as an adhesion molecule [18]	Non-fibrillar collagen	Transmembrane collagen
Collagen XIV	Abundant in the embryonic stage, strong ECM interactions	Regulate early stages of fibrillogenesis [19]	Non-fibrillar collagen	FACIT
Collagen XV	Low abundance	Structural link between producing cells and connective tissues [20]	Non-fibrillar collagen	Multiplexing
Collagen XVI	Abundant in the embryonic stage, strong ECM interactions	Support interaction of connective tissue cells with their ECM [21]	Non-fibrillar collagen	FACIT
Collagen XVII	Transmembrane nature	Facilitate epidermal-dermal attachment, a niche for hair follicle stem cells [22]	Non-fibrillar collagen	Transmembrane collagen
Collagen XVIII	Abundant in the embryonic stage	Control blood vessel formation [23]	Non-fibrillar collagen	Multiplexing
Collagen XIX	Low abundance, strong ECM interaction	Unknown functions. Suggest the regulation of cardiac extracellular matrix structure [24]	Non-fibrillar collagen	FACIT
Collagen XX	Low abundance, strong ECM interaction	Unknown functions. It may serve as a biomarker of solid tumors [25]	Non-fibrillar collagen	FACIT
Collagen XXI	Low abundance, strong ECM interaction	Unknown functions. May contribute to the extracellular matrix assembly [26]	Non-fibrillar collagen	FACIT
Collagen XXII	Low abundance, strong ECM interaction	Act as a cell adhesion ligand for skin epithelial cells and fibroblasts [27]	Non-fibrillar collagen	FACIT

Collagen XXIII	Transmembrane nature	Unknown functions. An important biomarker for lung cancer [28]	Non-fibrillar collagen	Transmembrane collagen
Collagen XXIV	Low abundance, limited in developing bone, and strong ECM interactions	Promote fibrillogenesis in bone and cornea [29]	Fibrillar collagen	Fibril-forming collagen
Collagen XXV	Low abundance, strong ECM interaction	Promote fusion of myoblasts into myofibers [30]	Non-fibrillar collagen	Transmembrane collagen
Collagen XXVII	Low abundance	Unknown functions. Suggest to support testis and ovary development [31]	Non-fibrillar collagen	FACIT
Collagen XXVII	Abundant in the embryonic stage	Support calcification of cartilage and the transition of cartilage to bone [32]	Fibrillar collagen [33]	Fibril-forming collagen
Collagen XXVIII	Low abundance	May contribute to neuron protection and support [34]	Non-fibrillar collagen	Fibril-forming collagen

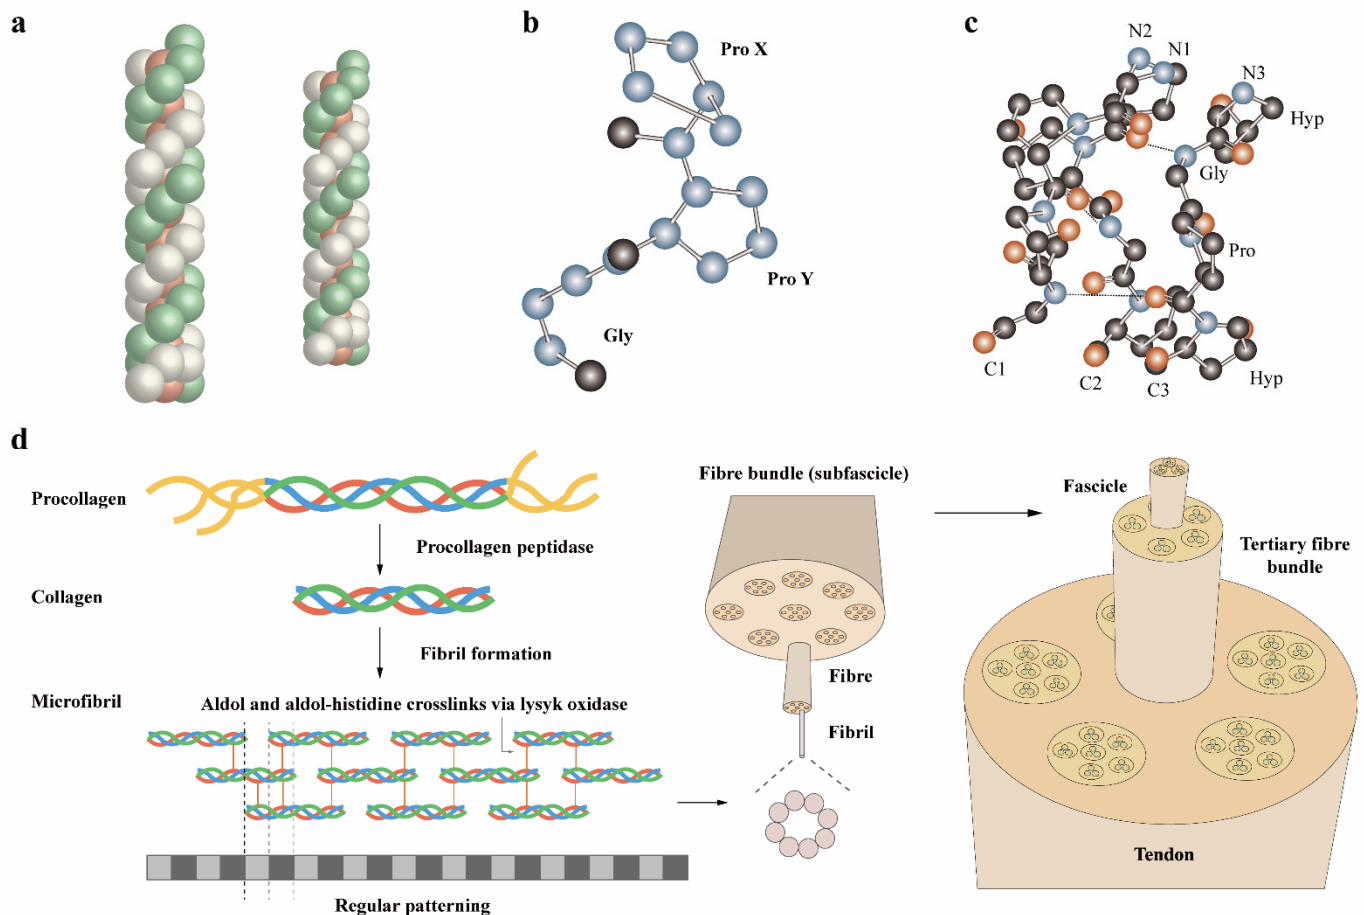


Figure 1. Fibrillar collagen assembly and the collagen triple helix: **(a)** Structure of triple helix, consisting of the repeating (ProHypGly)₄-(ProHypAla)-(ProHypGly)₅ sequence [35]. **(b)** ProX-ProY-Gly chain in collagen triple helix [36]. **(c)** Three strands in the collagen triple helix stagger together and form a ladder-like pattern of hydrogen bonds. **(d)** The biosynthesis of collagen begins with procollagen. Collagen molecules assemble into microfibrils in the extracellular matrix [37,38].

Collagen plays a pivotal role in mediating interactions between cell and the ECM [39]. A triple-helical domain characterizes fibrillar collagen. Other collagen types, such as fibril-associated collagen with interrupted triple helices (FACIT), demonstrate the interspersed triple-helical domains within non-collagenous (NC) domains. These NC domains are crucial for structural assembly and confer biological activity to collagen [40].

1.1. Fibrillar Collagen

Fibrillar collagen exhibits a hierarchical structure wherein parallel staggered collagen molecules self-assemble into fibrous nanostructures that further aggregate into higher-order assemblies [41]. Synthesis begins with the production of procollagen precursors containing carboxy-terminal propeptides and signal sequences that direct trafficking to the rough endoplasmic reticulum (ER) [42]. Within the ER, propeptides undergo hydroxylation of lysine and proline residues by lysyl and prolyl hydroxylases, respectively [42]. Proline and hydroxyproline play a crucial role in stabilizing the triple helix [43,44]. Following lysyl hydroxylation and O-linked glycosylation, α -chains trimerize into procollagen, a process initiated by the C-propeptide domain. This domain recognizes α -chains via a specialized mechanism, forming a stable core that drives triple helix assembly [45–47].

The formation of collagen microfibrils involves the nucleation, organization, and unidirectional elongation of short primary nanofibers (Figure 1) [48,49], which subsequently merge to form microfibrils exhibiting increased longitudinal and axial dimensions [50,51]. These supramolecular assemblies undergo stabilization via covalent crosslinking [52], a process initiated by extracellular lysine oxidases that catalyze the oxidative deamination of lysine residues in target peptides [53]. Within the microfibrils, the N- and C-termini of adjacent collagen monomers interact and are covalently cross-linked by lysyl oxidase, further enhancing structural stability [53,54]. Ultimately, the assembly of collagen microfibrils depends on the complex interplay of chemical and physical interactions among its components [55].

1.2. Non-Fibrillar Collagen

The collagen family also includes non-fibrillar members, such as network-forming collagen IV, which assemble into sheet-like networks rather than fibers [56]. These collagen IV networks have been vital to the evolution of multicellular organisms [57]. Collagen IV differs from fibrillar collagen in two key aspects of its higher-order assembly [58]. First, the C-terminal non-collagenous (NC1) domain of collagen IV is retained during assembly and plays a central role in network formation [9,59]. Second, collagen IV features a sequence with a discontinuity in the (Gly-X-Y)_n repeat, where glycine is absent or replaced in one of the three residues. This disrupts the formation of continuous triple-helical regions and creates local structural instability [60], a feature also seen in other non-fibrillar collagens [4].

The assembly of collagen IV scaffolds is a complex process. Intracellular enzymes collaborate to construct the heterotrimer, but the assembly into a three-dimensional (3D) scaffold occurs extracellularly. After secretion, protomers align via their NC1 and 7S domains, forming critical junctions at the protofibril ends. The triple helix then undergoes superhelical formation through lateral interactions [61]. During this process, functional molecules are incorporated into the collagen triple helix by embedding binding sites along the protofibril length. These network-forming collagens act as “smart” scaffolds, especially as components of the basement membrane, supporting the development and function of multicellular tissues [9].

1.3. Biological Function of Collagen

Collagen is vital in modulating a range of signaling pathways essential for development, regeneration, and tissue repair, thus maintaining tissue homeostasis. Its interaction with cells is primarily mediated by specific receptors facilitating bidirectional transmission of mechanical and biochemical signals through cytoskeleton-mediated processes (Table 2). Key receptors include integrins and discoidin domain receptors (DDR1 and DDR2) [62,63].

Integrins are heterodimeric receptors present on nearly all cell types and serve as major mediators for extracellular matrix components, including collagen. They play pivotal roles in regulating cell signaling, migration, survival, and differentiation [63,64]. Four collagen-binding integrins, $\alpha 1\beta 1$, $\alpha 2\beta 1$, $\alpha 10\beta 1$, and $\alpha 11\beta 1$, have been identified within the integrin $\alpha 1$ domain subgroup [65–67]. Although they share the function of collagen receptors, they are expressed in different cell types and mediate distinct biochemical signals. For example, $\alpha 1\beta 1$ integrin interacting with collagen triggers biological responses such as Grb2 recruitment, MAPK activation for cell proliferation, FAK phosphorylation facilitating fibroblast-to-myofibroblast differentiation, and activation of the Shc-mediated pathway in skin regeneration.

Receptor tyrosine kinases, especially DDR1 and DDR2, are also activated upon collagen binding [68,69]. DDR1 is mainly expressed in epithelial cells, while DDR2 is found in fibroblasts and mesenchymal cells. Unlike integrins, DDRs mediate ECM signaling unidirectionally. DDR2's interaction with collagen II is indirectly regulated by integrin/cytokine pathways and AGE-mediated signaling [70,71]. DDR2-bound collagen in the ECM activates the JNK/MAPK and PI3K/Akt pathways, influencing cell proliferation, survival, and gene expression. DDR1 binding to collagen activates JNK, NF- κ B, p38, ERK1/2 MAPKs, and PI3K/Akt signaling pathways. DDR1 inactivation leads to interactions with E-cadherin, promoting cell-cell contact. Both collagen-mediated cell-matrix communication and collagen-independent cell-cell interactions influence the triggering of diverse signaling pathways through DDRs [72].

Table 2. Receptors related to Collagen.

Receptor	Type	Distribution	Biological Regulation	Ligand Binding Specificity
Integrins	$\alpha 1\beta 1$	Fibroblasts, Mesenchymal tissues	Wound healing; Regulates the proliferation of living cells, MMP expression, and collagen synthesis; Fibroblast to myofibroblast differentiation; Invasion and growth of hepatocellular carcinoma	Collagens I, III, IV, IX, XIII, XVI, and the collagen IV chain–derived peptide arresten [73–75]
	$\alpha 2\beta 1$	Platelets, epithelium, Fibroblasts, and Mesenchymal tissues	Platelet adhesion to collagen; Hepatocellular carcinoma invasion and growth; Wound healing	Collagens I, III, IV, V, XI, XVI, and XXIII [76–78]
	$\alpha 10\beta 1$	Cartilage and Chondrocytes	Chondrogenic differentiation; Cartilage repair, Skeletal growth	Collagen II and IX [78]
	$\alpha 11\beta 1$	Periodontal ligaments	Wound healing; Cell migration; Mediates the contraction of collagen lattices; Myofibroblast differentiation	Collagen I and XIII [79,80]
Receptor Tyrosine Kinases (DDR)	DDR1	Epithelial cells, Smooth muscle cells, Fibroblasts, Oligodendrocytes and Macrophages	Development and growth of organs; Cell proliferation, survival, homing, and colonization; Inhibits tumor growth	Collagen I–V [81]
	DDR2	Chondrocytes	Development and growth of organs; Development of bone and cartilages; Pathological process of arthritis, wound healing, dwarfism, and tumor	Collagen I–III, and V[81]
Immunoglobulin Receptor	GPVI	Megakaryocytes and Platelets	Wound healing	Collagen I–III [82]
	OSCAR	A wide range of myeloid cells	Osteoclast growth induction for bone resorption; Osteoclast differentiation	Collagen I and II [83]
Leukocyte Receptor Complex (LRC)	LRC	Immune cells	Autoimmunity; Antiviral immunity; Graft tolerance; Regulates osteoclast differentiation.	Collagen I and III [84]
Other Receptors	Fibronectin	Extracellular matrix, Plasma, and Cell surface	Tissue growth; Wound repair; Fibroblast migration; Nerve regeneration stabilization; Extracellular matrix and embryogenesis; cell-to-cell adhesion	Collagen I and III [85]
	Vitronectin	Extracellular matrix, Blood serum, Platelets, and Bone.	Cell proliferation; Adhesion; Immune defense; Hemostasis; Fibrinolysis	Collagen I [86]
	uPARAP	Mesenchymal cell surface, Osteocytes, and Osteoblasts	Fibroblast migration; Primary adhesion of collagen to fibroblasts	Collagen I, II, IV, and V [87]

GPVI: Glycoprotein VI; OSCAR: Human osteoclast-associated receptor.

2. From Native Collagen to Protein Engineering

The isolation of collagen from natural tissues laid the foundation for its application in biomedicine, yet the inherent limitations of native collagen extraction have catalyzed the evolution toward engineered alternatives. Pioneering work by Lister and Macewen utilizing sheep intestinal collagen sutures [4,88] established collagen's biocompatibility, while its subsequent use as cell culture matrices [89] revealed structural dependency on tissue-specific supramolecular assemblies [90,91].

Traditional extraction protocols predominantly utilize mammalian sources like bovine, pig skin, and rat tail tendon, and marine byproducts like fish through acidic/alkaline hydrolysis or enzymatic digestion [92–94]. Collagen from bovine Achilles tendon [95,96] and porcine skin [97] dominated early biomaterial development [98–100].

Acid and alkaline extraction methodologies inevitably perturb these critical structural determinants through three primary mechanisms (Figure 2). First, thermal denaturation at temperatures exceeding 40°C induces unwinding of the triple helix into disordered random coils, leading to an 85% reduction in tensile strength compared to native fibrillar collagen [90]. Second, enzymatic hydrolysis using proteases such as pepsin preferentially cleaves non-helical telopeptide regions, generating fragmented polypeptides (3–6 kDa) with compromised cell-binding RGD motifs essential for integrin-mediated signaling [101–103]. Third, the hydrolysis of lysyl oxidase-catalyzed pyridinoline crosslinks, as evidenced by the decrease in Young's modulus [99].

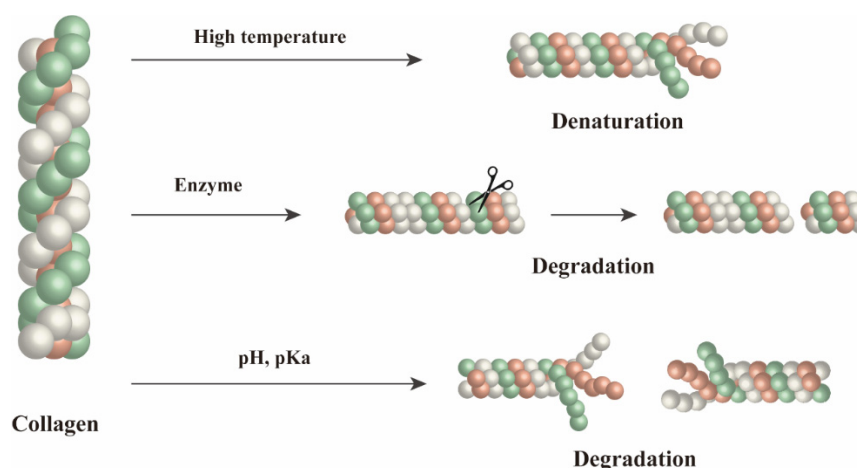


Figure 2. Structural Degradation During Natural Collagen Extraction: There are three principal mechanisms that compromise collagen's structural integrity during the extraction process: thermal denaturation, enzymatic hydrolysis, and cross-link disruption.

To overcome these limitations, collagen mimetic peptides (CMPs) have emerged as engineered alternatives that recapitulate core triple-helical motifs while enabling programmable functionality. Recent advances demonstrate that CMPs can be rationally designed to resist thermal denaturation through strategic incorporation of unnatural amino acids or covalent cross-linking [104]. Notably, π -system end-capping strategies stabilize short CMPs with only 3–6 repeats, achieving melting temperatures up to 76 °C [105]. Furthermore, functional domains (e.g., GFOGER for integrin binding) can be embedded without disrupting fibril morphology, restoring cell-adhesion activity lost in enzymatically hydrolyzed collagen fragments [106,107]. These approaches collectively enable the synthesis of chemically complex, well-controlled collagen mimetic biomaterials.

3. Biological Synthesis of Recombinant Collagen

The drawbacks of native collagen extraction, such as the risk of pathogen transmission, immunogenicity, structural heterogeneity, and limited scalability, have prompted a shift toward recombinant collagen production [108] (Table 3). Recombinant strategies enable control over amino acid sequence, post-translational modifications (PTMs), and molecular architecture, allowing the fabrication of collagen with tunable properties (Figure 3). *Escherichia coli* is widely favored among expression systems for its rapid proliferation, low production cost, and high-density fermentation capability [109]. However, the lack of endogenous prolyl-4-hydroxylase (P4H) in *E. coli* impairs hydroxyproline synthesis, thereby limiting triple-helix thermal stability [110]. To overcome this, researchers have implemented heterologous coexpression of P4HA and P4HB from *Caenorhabditis elegans*, increasing hydroxyproline content to 15% and raising the collagen melting temperature (T_m) by approximately 7 °C [111–113]. Further enhancements involve

rational sequence engineering, extending Gly-X-Y repeats from 20 to 40 units to improve interchain packing, and the fusion of elastin-like polypeptides (ELPs) to the N-terminus [114], enabling temperature-responsive trimerization with over 80% efficiency at physiological temperature [115].

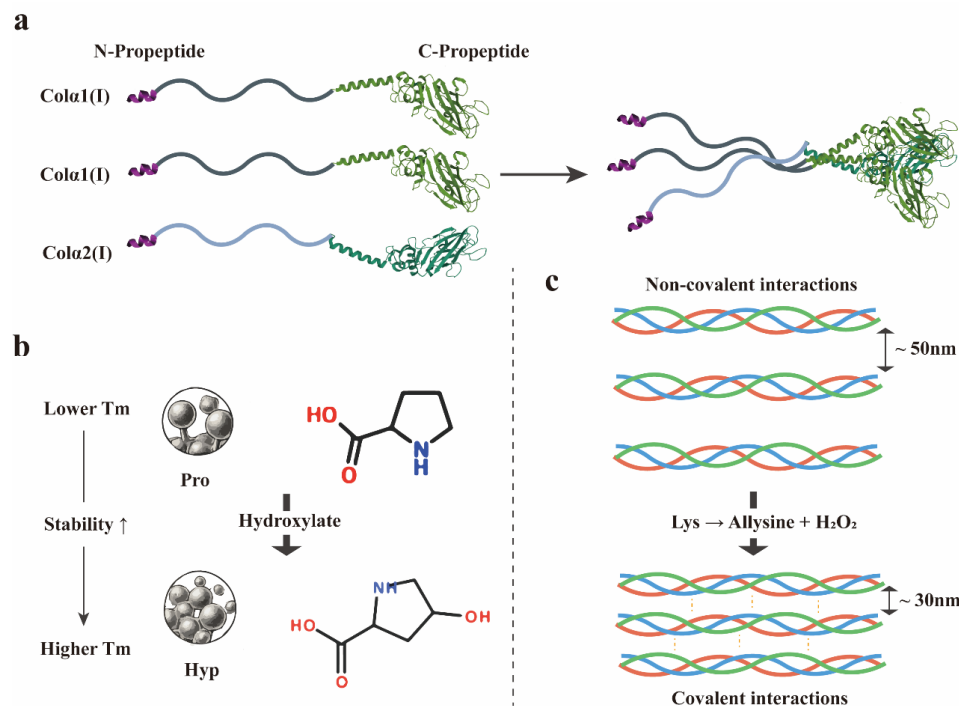


Figure 3. Protein Engineering Strategies for Collagen Stabilization: **(a)** C-propeptide-mediated heterotrimeric assembly of type I collagen. **(b)** Hydroxyproline-mediated stabilization of triple-helix thermodynamics. **(c)** Enzymatic crosslinking enhances fibrillar shear resistance.

Yeast expression systems, particularly *Pichia pastoris*, offer a more conducive environment for collagen biosynthesis with appropriate PTMs. Coexpression of human P4HA1/P4HB achieves hydroxyproline levels up to 88% of native collagen [116,117] while optimized dual-promoter constructs allow stoichiometric expression of pro- α 1 (I) and pro- α 2 (I) chains for heterotrimer formation [118]. Nonetheless, purification of heterotrimers at >65% remains a technical challenge. Industrial-scale fed-batch fermentation faces challenges in dissolved oxygen management, where maintaining >30% saturation without oxidative stress requires fine-tuned bioreactor control. Additionally, the production process in yeast systems often requires strict control of methanol induction, pH stability, and osmolarity to avoid protein aggregation and ensure correct folding. These parameters are dynamically regulated through feedback-controlled fermentation systems integrating real-time methanol sensing, DO and pH monitoring, and osmotic pressure balancing. Strategies such as pulse-wise methanol feeding (1.0–2.0 g/L), pH stabilization at 5.0 ± 0.1 , and osmolyte supplementation (e.g., sorbitol, betaine) have enhanced solubility and reduced aggregation [117]. Additionally, additives like sodium pyruvate can boost TCA cycle flux, increasing collagen yield by over 20% and shortening induction time. Industrial-scale systems often employ high-density fed-batch protocols (>150 g DCW/L) with optimized agitation-oxygen transfer to maintain protein quality [119]. Use of engineered strains with enhanced secretory pathways, or those co-expressing molecular chaperones, has shown promise in improving the yield and solubility of full-length collagen proteins. Recent progress also includes the coexpression of lysyl oxidase homologs (e.g., LOXL2) [120] to introduce enzymatic crosslinking and targeted N-glycosylation at Asn-X-Ser motifs to improve proteolytic resistance and in vivo stability [121]. Moreover, in vitro hydroxylation using purified P4H enzymes has emerged as a complementary strategy for microbial-expressed collagen, allowing post-expression modification of Hyp content without the need for endogenous enzymatic activity. (Figure 4) Mammalian expression systems such as CHO and HEK293 cells represent the advancements for producing recombinant collagen with near-native fidelity, particularly in PTMs and structural assembly [122–124]. The production cost remains higher than that of microbial systems, limiting application in high-volume products such as scaffold matrices. Emerging alternatives include stem cell-derived extracellular matrix secretion without genetic modification, wherein extracellular niche modulation induces the synthesis of human ECM collagen (hCol) with native-like molecular weights (α 1 ~132 kDa; α 2 ~122 kDa),

glycosylation profiles, and fibrillar periodicity [124]. This strategy bypasses transgene-associated regulatory hurdles and offers immunologically safer products. Regarding function and safety, the residues of terminal peptides and non-human glycosylation may trigger an immune response. Studies have been conducted to remove N/C-terminal propeptide and telopeptide from recombinant type I collagen, and the endotoxin is controlled within 0.05 EU/mg to ensure the function and safety [125,126].

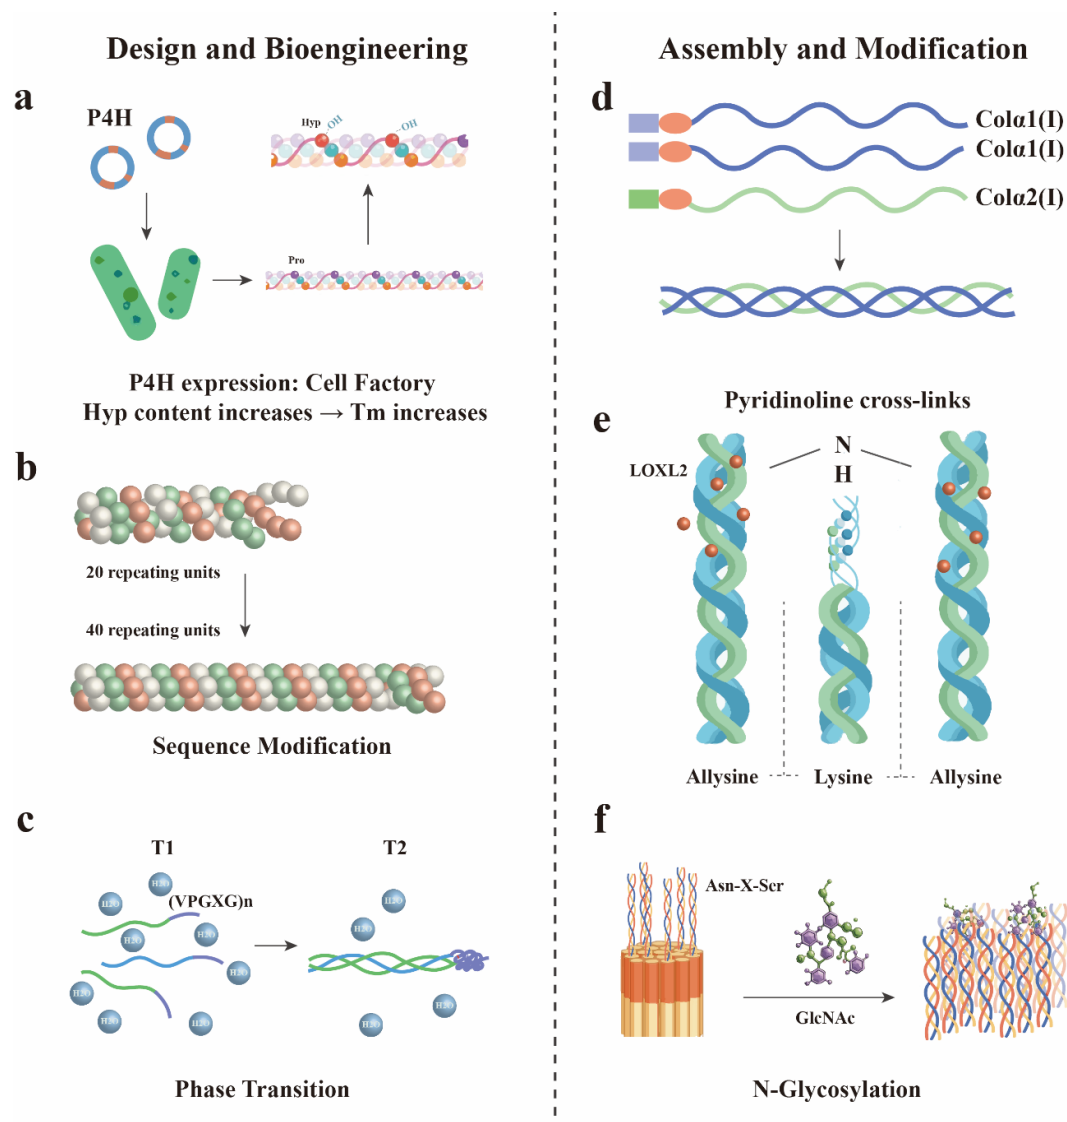


Figure 4. Engineering Strategies for Collagen Biosynthesis. Design and engineering: (a) Cell factory for P4H expression; (b) Sequence Modification; (c) ELP phase separation. Assembly and Modification: (d) Chain Stoichiometry Control; (e) LOXL2-Mediated Crosslinking; (f) Directed N-Glycosylation.

Complementing these bioproduction systems, synthetic biology and AI-guided protein design rapidly advance collagen engineering. Platforms such as ColDiff and ColGen-GA apply diffusion-based modeling and genetic algorithms to design stable, self-assembling collagen variants with tailored biofunctions [127]. AI-assisted strategies in collagen sequence design, structure prediction, and assembly optimization are illustrated in Section 4. These tools enable the rational construction of collagen domains for diverse biomedical applications [128]. Beyond domain-level sequence design, AI-driven simulation platforms now integrate structural dynamics and protein interaction predictions to assess fibrillogenesis potential or improve integrin-binding affinity.

Collectively, recent breakthroughs such as the development of self-assembling recombinant collagen hydrogels without chemical crosslinkers [129,130], high-temperature-resistant triple helix structures stabilized by cold-adapted chaperones, and coexpression of folding enhancers have substantially addressed many technical barriers [131,132]. However, challenges remain in ensuring batch consistency, achieving uniform post-translational modifications, and meeting regulatory standards for clinical application.

Table 3. The fabrication and biosynthesis of collagen.

Type of Collagen	Host	Yield	Comments	Concerned Contaminants
Natural Collagen	—	—	Obtained by enzymatic action; Immunogenicity, pathogen transmission issues; Human collagen extraction is limited and expensive	Residual host proteins; chemical residues; pathogenic microorganisms [92]
Recombinant Human Collagen	<i>E. coli</i>	90 mg/L	Coexpression with mimivirus prolyl and lysyl hydroxylases	Endotoxins (from <i>E. coli</i> LPS); media residues [113]
	<i>P. pastoris</i>	0.6 g/L	Coexpression with human prolyl hydroxylases in a bioreactor with constant oxygen supply	Cell wall components (β -glucans, Mannans); media residues [117]
	<i>Mammalian cells (293-EBNA)</i>	0.5–80 mg/L	Coexpression with P4H subunits is not required except for collagens X and VIII expression. Low yields of collagen V heterotrimers	Mycoplasma contamination; Viral contaminants [121,127]
	<i>Plants (tobacco)</i>	30 mg/kg	Coexpression with P4H subunits to obtain hydroxylated collagen	Mycotoxins and contaminants from fungal infections; heavy metals; pesticides/herbicides [114,116]
	<i>Transgenic maize seeds</i>	4 mg/kg; 12 mg/kg	Co-expressed with/without both the α - and β -subunits of a recombinant human P4H (rP4H).	
	<i>Drosophila melanogaster S2 cells</i>	10–50 mg/L	Production of collagen I and IX heterotrimers	Mycoplasma contamination; distinct glycosylated products [133,134]

4. AI-Assisted Design and Modeling of Collagen

4.1. Advances in AI-Driven Protein Engineering

Recent advances in deep learning have enabled the *de novo* design of synthetic collagen with programmable properties. ProtSeed, a sequence-structure co-design framework, has shown a 3.2-fold increase in heterotrimer assembly efficiency over random sequences by optimizing charge complementarity and steric compatibility at glycine-X-Y junction [135]. Progress in deep learning has transformed collagen structural prediction and design. The AlphaFold Multimer model has shown excellent performance in predicting protein complex structures, with prediction accuracies of 67% and 69% at the interface between hetero and homo oligomers, respectively, when tested on 4433 protein complexes [136]. The progress in geometric deep learning and the application of models have enhanced our ability to predict and design collagen structures, leading to the development of new collagen-based materials and therapies with tailored properties.[137–139]

4.2. AI-Assisting Design of Collagen Variants

Generative artificial intelligence (AI) technologies have opened new window for the *de novo* design of collagen. Tools based on autoregressive models and Transformer architectures [131–133], such as ProteinMPNN [140] and ESM-IF [141], have enhanced sequence design precision by integrating geometric features, such as torsion angles and backbone vectors, and geometric vector perceptrons (GVPs), particularly excelling in tasks requiring sub-nanoscale control, such as collagen fibril assembly [142]. For instance, the diffusion model ColDiff, combined with a supervised learning strategy, extracts sequence features from human collagen multi-omics data to generate collagen-mimetic peptides (CMPs) with GXY repeat structures, achieving a Pearson correlation of up to 0.95 (natural collagen) and 0.8 (synthetic CMPs) between predicted and experimental melting temperatures (T_m) [143]. Additionally, the synergistic application of genetic algorithms (GA) and deep learning, like ColGen-GA, enables rapid generation of homotrimeric type I collagen sequences (1000 sequences in 8 h), with T_m prediction errors less than 5%, outperforming traditional molecular dynamics simulations [144].

Sequence design based on generative models requires modular strategies combined with experimental validation to optimize biological functionality. The adhesion module guides self-assembly into periodic banded fibers through hydrophobic or electrostatic interactions, while the functional module, based on Streptococcus Scl2 collagen-like protein fragments, introduces osteoblast-binding domains without disrupting fiber morphology [145]. Coarse-grained simulations and atomic modeling elucidate the hierarchical assembly of collagen triple helices into fibrils via gap-overlap stacking, consistent with experimental observations [146,147]. Experimental validation shows that such synthetic collagen achieves tensile strength approaching 50 MPa comparable to natural type I collagen and promotes osteogenic precursor cell differentiation, increasing alkaline phosphatase activity by over 2-fold [148]. Computational design strategies (e.g., reinforcement learning) enable the generation of collagen-mimetic peptides (CMPs) with high self-assembly propensity, though experimental validation remains critical [149]. Short CMPs can form hydrogels at low concentrations, while long-chain variants require proline hydroxylation (up to 90% in yeast systems) for conformational stability [143], highlighting the necessity of post-translational modifications in biomimetic design.

4.3. AI-Assisting Optimization of Collagen Protein

AI technologies enable quantitative optimization of collagen material properties through high-throughput screening and molecular engineering strategies. The ColGen-GA framework identifies key GXY triplets contributing to thermal stability by analyzing millions of generated sequences: sequences containing (GPO)₁₄ exhibit the lowest ΔT_m values (T_m reduction of 3 °C) [144]. Experimental validation further demonstrates that AI-designed recombinant CMPs achieve secretion efficiencies of 0.1–0.2 mg/mL in *Pichia pastoris*, with characteristic CD spectral peaks at 220–222 nm and a 40% improvement in cell adhesion efficiency compared to traditional collagen. Moreover, AI-driven optimization of collagen extraction processes, such as enzyme concentration, temperature, and pH value, reduces energy consumption by 40% and waste by 45%, while enabling collagen recovery from waste materials such as fish scales and bovine hides, showcasing end-to-end efficiency from molecular design to industrial production [150,151]. Future efforts should focus on integrating multimodal data, sequence-structure-function, to enhance model generalizability and leveraging automated experimental platforms, such as iBioFoundry, to complete the “design-synthesis-testing” loop [152].

5. Engineering on Collagen Biomaterials

Contemporary molecular engineering strategies enable the precise customization of collagen biomaterials through domain-specific modifications and advanced crosslinking architectures. These approaches have unlocked transformative potential for synthetic collagens across a range of biomedical applications (Table 4). For example, incorporating cell-binding RGD motifs or MMP-sensitive cleavage sites into collagen scaffolds improves cell-material interactions, a fibrinogen-collagen hybrid hydrogel demonstrated a minimum wound closure rate of 83.3% compared to natural collagen with 69.4% [153]. Similarly, VEGF peptide-functionalized scaffolds enhance vascular regeneration by increasing surface wettability, inducing VEGF receptor phosphorylation, and promoting HUVEC survival and proliferation [154]. These scaffolds, fabricated via simple polymer mixing methods, hold promise for sustaining endothelial cell viability during vascular network formation, potentially improving transplanted tissue survival rates. Beyond regenerative medicine, engineered collagens are facilitating oncology research. Collagen-based 3D tumor models with tunable stiffness recapitulate tumor microenvironment mechanics, enhancing immune checkpoint marker expression and aligning drug response profiles with clinical observations [155,156]. The aberrant crosslinking in pathological matrices revealed by AGE mediated collagen fiber binding in liver cirrhosis, can impair remodeling ability. The fibers crosslinked by AGE form coarse bundles, with a 3-fold increase in diameter and a 60% decrease in macrophage remodeling efficiency, promoting fibrosis progression through cytoskeletal disorder and type II immune polarization [157]. This emphasizes the necessity of precise crosslinking control in engineering supports.

Beyond its conventional biomedical applications, recombinant collagen emerges as a transformative material in intelligent drug delivery systems and tissue engineering. Recent technological advancements have capitalized on collagen's programmable biodegradability to develop stimuli-responsive nanocarriers. pH-sensitive collagen nanocapsules have demonstrated remarkable tumor-specific drug release efficiency, achieving 90% drug release through lysosomal acidity-triggered dissolution at pH 5.5 [158]. Light-responsive elastin-like peptide nanoparticles have enabled spatiotemporal control of targeted cellular delivery through near-infrared-induced phase transitions, enhancing targeting efficacy by two-fold [159].

In the realm of tissue engineering, recombinant collagen has exhibited good biocompatibility and cell activity promotion in skin wound repair applications. The incorporation of recombinant collagen into GelMA (gelatin methacryloyl) has enhanced cellular activity and migration capacity, thereby accelerating wound healing processes [160]. *In vivo* experiments demonstrated that wounds treated with recombinant collagen-modified GelMA achieved an 80% healing rate within 14 days, representing a 1.2-fold improvement compared to untreated diabetic mice. The mechanical and self-healing properties of collagen-based hydrogels can be optimized through the strategic network and chain topology design [161–163]. The mechanical optimization carried out through network topology design now combines with a hyperelastic framework, with a self-recovery rate of >95% after 500 cycles, and a compression tension elastic ratio adjusted to 1.5, approaching natural tissue characteristics [164].

Table 4. Biomedical Applications of Collagen-based Biomaterials.

Applications	Tissue	Origin	Crosslinking Agents	Bioharzard of Crosslinking Agents
Wound dressing	Epidermal and dermal acellular scaffolds	Synthetic/ Natural	1,4-butanediol diglycidyl ether (BDDGE)/ EDC	Contact dermatitis, allergic[120,121]
	Hydrogels based on human-like collagen and carboxyl pullulan	Synthetic	Butanediol-diglycidyl ether (BDDE)	
Tendon Repair	Collagen-glycosaminoglycan scaffold		Acrylonitrile butadiene styrene (ABS)	Not an irritant [165]
Treatment of Intervertebral Disc Degeneration and Cartilage Repair	Fibrillized jellyfish collagen and alginate hydrogel	Natural	EDC	Skin irritant [122]
	Self-assembled fibrocartilage	Natural	Lysyl oxidase like-2 (LOXL-2)	Not an irritant [166]
	Type II collagen-hyaluronic acid hydrogel	Synthetic	EDC	Skin irritant [167]
	Type II collagen scaffold/chondroitin sulfate composite gel	Natural	Genipin	LD50: 237 mg/kg (oral route) for mice [168–170]
Drug Delivery	Growth factor-conjugated fibrin microbeads	Synthetic	Genipin	
	Collagen-hydroxyapatite scaffolds/Collagen-chitosan-graphene oxide mixture	Synthetic	EDC/N-hydroxysuccinimide (NHS)	An irritant/harmful by ingestion [171,172]
Treatment of Cardiovascular Diseases	Bovine pericardial		Dye-mediated photooxidation	Not an irritant [173]
	Decellularized carotids from a newborn calf	Synthetic/ Natural	Co-crosslinking with procyanidins and glutaraldehyde	Skin irritant; may induce asthma [142]
	Alginategelatin-polysaccharide scaffold	Synthetic	Glutaraldehyde	Skin irritant; may induce asthma [174]
	Decellularized osteochondral plug from pigs	Natural	Epigallocatechin-3 gallate (EGCG)	Not an irritant [137]
Bone Tissue Engineering	Recombinant peptide based on human collagen type I	Synthetic/ Natural	Hexamethylene diisocyanate/ Genipin	Skin irritant/LD50: 237 mg/kg (oral route) for mice [138]
	Collagen-glycosaminoglycan scaffold with/without mineral content	Synthetic	EDC/NHS	An irritant/ harmful by ingestion [139]
Neural Tissue Engineering	Collagen/Heparin sulfate scaffold		UV light [175]	
	Type I collagen from tendons	Natural/ Synthetic	Genipin/Glutaraldehyde	LD50: 237 mg/kg (oral route) for mice /skin irritant; may induce asthma [140,176]
	Type I/II collagen composite scaffold	Synthetic	EDC	Skin irritant [141]
Tissue Regeneration	Collagen scaffold	Synthetic	Sulfosuccinimidyl 4-(N-maleimidomethyl) cyclohexane-1-carboxylate	Skin irritant [177]
	type I collagen	Natural	Riboflavin 5' monophosphate (FMN)	Not an irritant [178]
Treatment of corneal diseases	Enucleated rabbit corneas		Rose bengal and green light [179]	
Dentistry	Demineralized human dentin	Natural	Plant-derived polyphenols [180]	
	Bovine collagen	Natural	Epicatechin	Skin irritant [181]

6. Summary and Perspectives

Collagen, the most abundant structural protein in the human body, has become a cornerstone of biomedical engineering. Its hierarchical architecture, biocompatibility, and multifunctional versatility make it highly valuable. This review traces collagen's evolution from its native biological roles to its applications in engineered biomaterials, focusing on molecular design principles, synthetic strategies, and computational innovations that overcome the limitations of natural collagen extraction. Key advancements include developing recombinant expression systems with enhanced thermal stability and AI-driven design platforms exploring new biomaterials.

The integration of computational design, synthetic biology, and advanced manufacturing is pioneering collagen engineering. Next-generation collagen materials programmable in mechanics, biodegradation, and bioactivity will be transferred into regenerative medicine, oncology models, and smart drug delivery systems. However, achieving this vision requires interdisciplinary progress to align molecular-scale innovation with clinical and industrial requirements.

Acknowledgments

We also would like to thank the iBiofoundary and Core Facility of Institute for Intelligent Bio/Chem Manufacturing, and ZJU-Hangzhou Global Scientific and Technological Innovation Center, Zhejiang University.

Author Contributions

Conceptualization, Y.Y. and X.Z.; Software, Z.W. and C.Z.; Writing—Original Draft Preparation, X.Z.; Writing—Review & Editing, X.Z., Y.Y. and Q.Z., X.L., B.L.; Visualization, X.Z.; Supervision, Y.Y.; Project Administration, Y.Y.; Funding Acquisition, Y.Y.

Ethics Statement

Not applicable.

Informed Consent Statement

Not applicable.

Data Availability Statement

The datasets generated during the current study are available from the corresponding author on reasonable request.

Funding

This research was supported by Zhejiang Provincial Natural Science Foundation of China under Grant (No. LR25C100001), 'Pioneer' and 'Leading Goose' R&D Program of Zhejiang Province (No. 2025C01100, No. 2025C01102), the National Natural Science Foundation of China General Program (No.32471372).

Declaration of Competing Interest

The authors declare that they have no competing interests.

References

1. Granito RN, Custódio MR, Rennó ACM. Natural Marine Sponges for Bone Tissue Engineering: The State of Art and Future Perspectives. *J. Biomed. Mater. Res. B Appl. Biomater.* **2017**, *105*, 1717–1727. doi:10.1002/jbm.b.33706.
2. Viguet-Carrin S, Garnero P, Delmas PD. The Role of Collagen in Bone Strength. *Osteoporos. Int.* **2006**, *17*, 319–336. doi:10.1007/s00198-005-2035-9.
3. Ricard-Blum S. The Collagen Family. *Cold Spring Harb. Perspect. Biol.* **2011**, *3*, a004978. doi:10.1101/cshperspect.a004978.
4. Shoulders MD, Raines RT. Collagen Structure and Stability. *Annu. Rev. Biochem.* **2009**, *78*, 929–958. doi:10.1146/annurev.biochem.77.032207.120833.
5. Fallas JA, O'Leary LER, Hartgerink JD. Synthetic Collagen Mimics: Self-Assembly of Homotrimers, Heterotrimers and Higher Order Structures. *Chem. Soc. Rev.* **2010**, *39*, 3510. doi:10.1039/b919455j.
6. Kannus P. Structure of the Tendon Connective Tissue. *Scand. J. Med. Sci. Sports* **2000**, *10*, 312–320. doi:10.1034/j.1600-0838.2000.010006312.x.

7. Hu X, Wu Z, Zhang Z, Yao H, Wang D-A. Type II Collagen Scaffolds for Tissue Engineering. *Commun. Mater.* **2024**, *5*, 149. doi:10.1038/s43246-024-00598-x.
8. Kuivaniemi H, Tromp G. Type III Collagen (COL3A1): Gene and Protein Structure, Tissue Distribution, and Associated Diseases. *Gene* **2019**, *707*, 151–171. doi:10.1016/j.gene.2019.05.003.
9. Brown KL, Cummings CF, Vanacore RM, Hudson BG. Building Collagen IV Smart Scaffolds on the Outside of Cells. *Protein Sci.* **2017**, *26*, 2151–2161. doi:10.1002/pro.3283.
10. Malak TM, Ockleford CD, Bell SC, Dalgleish R, Bright N, Macvicar J. Confocal Immunofluorescence Localization of Collagen Types I, III, IV, V and VI and Their Ultrastructural Organization in Term Human Fetal Membranes. *Placenta* **1993**, *14*, 385–406. doi:10.1016/S0143-4004(05)80460-6.
11. Di Martino A, Cescon M, D'Agostino C, Schilardi F, Sabatelli P, Merlini L, et al. Collagen VI in the Musculoskeletal System. *Int. J. Mol. Sci.* **2023**, *24*, 5095. doi:10.3390/ijms24065095.
12. Chung HJ, Uitto J. Type VII Collagen: The Anchoring Fibril Protein at Fault in Dystrophic Epidermolysis Bullosa. *Dermatol. Clin.* **2010**, *28*, 93–105. doi:10.1016/j.det.2009.10.011.
13. Li Q, Tintut Y, Demer LL, Vazquez-Padron RI, Bendeck MP, Hsu JJ. Collagen VIII in Vascular Diseases. *Matrix Biol.* **2024**, *133*, 64–76. doi:10.1016/j.matbio.2024.08.006.
14. Carlsen S, Nandakumar KS, Holmdahl R. Type IX Collagen Deficiency Enhances the Binding of Cartilage-Specific Antibodies and Arthritis Severity. *Arthritis Res.* **2006**, *8*, R102.
15. Shen G. The Role of Type X Collagen in Facilitating and Regulating Endochondral Ossification of Articular Cartilage. *Orthod. Craniofac. Res.* **2005**, *8*, 11–17. doi:10.1111/j.1601-6343.2004.00308.x.
16. Sun M, Luo EY, Adams SM, Adams T, Ye Y, Shetye SS, et al. Collagen XI Regulates the Acquisition of Collagen Fibril Structure, Organization and Functional Properties in Tendon. *Matrix Biol.* **2020**, *94*, 77–94. doi:10.1016/j.matbio.2020.09.001.
17. Papanicolaou M, Parker AL, Yam M, Filipe EC, Wu SZ, Chitty JL, et al. Temporal Profiling of the Breast Tumour Microenvironment Reveals Collagen XII as a Driver of Metastasis. *Nat. Commun.* **2022**, *13*, 4587. doi:10.1038/s41467-022-32255-7.
18. Heikkinen A, Tu H, Pihlajaniemi T. Collagen XIII: A Type II Transmembrane Protein with Relevance to Musculoskeletal Tissues, Microvessels and Inflammation. *Int. J. Biochem. Cell Biol.* **2012**, *44*, 714–717. doi:10.1016/j.biocel.2012.01.024.
19. Tao G, Levay AK, Peacock JD, Huk DJ, Both SN, Purcell NH, et al. Collagen XIV Is Important for Growth and Structural Integrity of the Myocardium. *J. Mol. Cell. Cardiol.* **2012**, *53*, 626–638. doi:10.1016/j.yjmcc.2012.08.002.
20. Bretau S, Guillon E, Karppinen S-M, Pihlajaniemi T, Ruggiero F. Collagen XV, a Multifaceted Multiplexin Present across Tissues and Species. *Matrix Biol. Plus* **2020**, *6–7*, 100023. doi:10.1016/j.mbplus.2020.100023.
21. Grässel S, Bauer RJ. Collagen XVI in Health and Disease. *Matrix Biol.* **2013**, *32*, 64–73. doi:10.1016/j.matbio.2012.11.001.
22. Natsuga K, Watanabe M, Nishie W, Shimizu H. Life before and beyond Blistering: The Role of Collagen XVII in Epidermal Physiology. *Exp. Dermatol.* **2019**, *28*, 1135–1141. doi:10.1111/exd.13550.
23. Aikio M, Elamaa H, Vicente D, Izzi V, Kaur I, Seppinen L, et al. Specific Collagen XVIII Isoforms Promote Adipose Tissue Accrual via Mechanisms Determining Adipocyte Number and Affect Fat Deposition. *Proc. Natl. Acad. Sci. USA* **2014**, *111*, E3043–E3052. doi:10.1073/pnas.1405879111.
24. Sadri G, Fischer AG, Brittian KR, Elliott E, Nystoriak MA, Uchida S, et al. Collagen Type XIX Regulates Cardiac Extracellular Matrix Structure and Ventricular Function. *Matrix Biol.* **2022**, *109*, 49–69. doi:10.1016/j.matbio.2022.03.007.
25. Thorlacius-Ussing J, Jensen C, Madsen EA, Nissen NI, Manon-Jensen T, Chen IM, et al. Type XX Collagen Is Elevated in Circulation of Patients with Solid Tumors. *Int. J. Mol. Sci.* **2022**, *23*, 4144. doi:10.3390/ijms23084144.
26. Chou M-Y, Li H-C. Genomic Organization and Characterization of the Human Type XXI Collagen (COL21A1) Gene. *Genomics* **2002**, *79*, 395–401. doi:10.1006/geno.2002.6712.
27. Koch M, Schulze J, Hansen U, Ashwodd T, Keene DR, Brunken WJ, et al. A Novel Marker of Tissue Junctions, Collagen XXII. *J. Biol. Chem.* **2004**, *279*, 22514–22521. doi:10.1074/jbc.M400536200.
28. Kehlet SN, Karsdal MA. Type XXIII Collagen. In *Biochemistry of Collagens, Laminins and Elastin*; Elsevier: Amsterdam, The Netherlands, 2016; pp 139–141. doi:10.1016/B978-0-12-809847-9.00023-4.
29. Koch M, Laub F, Zhou P, Hahn RA, Tanaka S, Burgeson RE, et al. Collagen XXIV, a Vertebrate Fibrillar Collagen with Structural Features of Invertebrate Collagens. *J. Biol. Chem.* **2003**, *278*, 43236–43244. doi:10.1074/jbc.M302112200.
30. Gonçalves TJM, Boutillon F, Lefebvre S, Goffin V, Iwatsubo T, Wakabayashi T, et al. Collagen XXV Promotes Myoblast Fusion during Myogenic Differentiation and Muscle Formation. *Sci. Rep.* **2019**, *9*, 5878. doi:10.1038/s41598-019-42296-6.
31. Sato K, Yomogida K, Wada T, Yorihozi T, Nishimune Y, Hosokawa N, et al. Type XXVI Collagen, a New Member of the Collagen Family, Is Specifically Expressed in the Testis and Ovary. *J. Biol. Chem.* **2002**, *277*, 37678–37684. doi:10.1074/jbc.M205347200.
32. Hjorten R, Hansen U, Underwood RA, Telfer HE, Fernandes RJ, Krakow D, et al. Type XXVII Collagen at the Transition of Cartilage to Bone during Skeletogenesis. *Bone* **2007**, *41*, 535–542. doi:10.1016/j.bone.2007.06.024.
33. Exposito J-Y, Valcourt U, Cluzel C, Lethias C. The Fibrillar Collagen Family. *Int. J. Mol. Sci.* **2010**, *11*, 407–426.

- doi:10.3390/ijms11020407.
34. Grimal S, Puech S, Wagener R, Ventéo S, Carroll P, Fichard-Carroll A. Collagen XXVIII Is a Distinctive Component of the Peripheral Nervous System Nodes of Ranvier and Surrounds Nonmyelinating Glial Cells. *Glia* **2010**, *58*, 1977–1987. doi:10.1002/glia.21066.
35. Bella J, Eaton M, Brodsky B, Berman HM. Crystal and Molecular Structure of a Collagen-Like Peptide at 1.9 Å Resolution. *Science* **1994**, *266*, 75–81. doi:10.1126/science.7695699.
36. Berisio R, Vitagliano L, Mazzarella L, Zagari A. Crystal Structure of the Collagen Triple Helix Model [(Pro-Pro-Gly)₁₀]₃. *Protein Sci.* **2002**, *11*, 262–270. doi:10.1110/ps.32602.
37. Fan D, Takawale A, Lee J, Kassiri Z. Cardiac Fibroblasts, Fibrosis and Extracellular Matrix Remodeling in Heart Disease. *Fibrogenesis Tissue Repair* **2012**, *5*, 15. doi:10.1186/1755-1536-5-15.
38. Liu Y, Ramanath HS, Wang D-A. Tendon Tissue Engineering Using Scaffold Enhancing Strategies. *Trends Biotechnol.* **2008**, *26*, 201–209. doi:10.1016/j.tibtech.2008.01.003.
39. Tuckwell DS, Ayad S, Grant ME, Takigawa M, Humphries MJ. Conformation Dependence of Integrin-Type II Collagen Binding: Inability of Collagen Peptides to Support A2β1 Binding, and Mediation of Adhesion to Denatured Collagen by a Novel A5β1-Fibronectin Bridge. *J. Cell Sci.* **1994**, *107*, 993–1005. doi:10.1242/jcs.107.4.993.
40. Franzke C-W, Bruckner P, Bruckner-Tuderman L. Collagenous Transmembrane Proteins: Recent Insights into Biology and Pathology*. *J. Biol. Chem.* **2005**, *280*, 4005–4008. doi:10.1074/jbc.R400034200.
41. Mouw JK, Ou G, Weaver VM. Extracellular Matrix Assembly: A Multiscale Deconstruction. *Nat. Rev. Mol. Cell Biol.* **2014**, *15*, 771–785. doi:10.1038/nrm3902.
42. Myllyharju J. Intracellular Post-Translational Modifications of Collagens. In *Collagen*; Brinckmann J, Notbohm H, Müller PK, Eds.; Topics in Current Chemistry; Springer: Berlin/Heidelberg, Germany, 2005; Volume 247, pp. 115–147. doi:10.1007/b103821.
43. Persikov AV, Ramshaw JAM, Kirkpatrick A, Brodsky B. Electrostatic Interactions Involving Lysine Make Major Contributions to Collagen Triple-Helix Stability. *Biochemistry* **2005**, *44*, 1414–1422. doi:10.1021/bi048216r.
44. Brodsky B, Persikov AV. Molecular Structure of the Collagen Triple Helix. In *Advances in Protein Chemistry*; Elsevier: Amsterdam, The Netherlands, 2005; Volume 70, pp. 301–339. doi:10.1016/S0065-3233(05)70009-7.
45. Boudko SP, Engel J, Bächinger HP. The Crucial Role of Trimerization Domains in Collagen Folding. *Int. J. Biochem. Cell Biol.* **2012**, *44*, 21–32. doi:10.1016/j.biocel.2011.09.009.
46. McLaughlin SH, Bulleid NJ. Molecular recognition in procollagen chain assembly. *Matrix Biol.* **1998**, *16*, 369–377. doi:10.1016/s0945-053x(98)90010-5.
47. Bourhis J-M, Mariano N, Zhao Y, Harlos K, Exposito J-Y, Jones EY, et al. S. Structural Basis of Fibrillar Collagen Trimerization and Related Genetic Disorders. *Nat. Struct. Mol. Biol.* **2012**, *19*, 1031–1036. doi:10.1038/nsmb.2389.
48. Birk DE, Trelstad RL. Extracellular Compartments in Tendon Morphogenesis: Collagen Fibril, Bundle, and Macroaggregate Formation. *J. Cell Biol.* **1986**, *103*, 231–240.
49. Canty EG, Lu Y, Meadows RS, Shaw MK, Holmes DF, Kadler KE. Coalignment of Plasma Membrane Channels and Protrusions (Fibripositors) Specifies the Parallelism of Tendon. *J. Cell Biol.* **2004**, *165*, 553–563. doi:10.1083/jcb.200312071.
50. Bruckner P. Suprastructures of Extracellular Matrices: Paradigms of Functions Controlled by Aggregates Rather than Molecules. *Cell Tissue Res.* **2010**, *339*, 7–18. doi:10.1007/s00441-009-0864-0.
51. Wenstrup RJ, Florer JB, Brunskill EW, Bell SM, Chervoneva I, Birk DE. Type V Collagen Controls the Initiation of Collagen Fibril Assembly. *J. Biol. Chem.* **2004**, *279*, 53331–53337. doi:10.1074/jbc.M409622200.
52. Eyre DR, Weis MA, Wu J-J. Advances in Collagen Cross-Link Analysis. *Methods* **2008**, *45*, 65–74. doi:10.1016/j.ymeth.2008.01.002.
53. Lucero HA, Kagan HM. Lysyl Oxidase: An Oxidative Enzyme and Effector of Cell Function. *Cell. Mol. Life Sci.* **2006**, *63*, 2304–2316. doi:10.1007/s00018-006-6149-9.
54. Orgel JP, Wess TJ, Miller A. The *in Situ* Conformation and Axial Location of the Intermolecular Cross-Linked Non-Helical Telopeptides of Type I Collagen. *Structure* **2000**, *8*, 137–142. doi:10.1016/S0969-2126(00)00089-7.
55. O’Leary LER, Fallas JA, Bakota EL, Kang MK, Hartgerink JD. Multi-Hierarchical Self-Assembly of a Collagen Mimetic Peptide from Triple Helix to Nanofibre and Hydrogel. *Nat. Chem.* **2011**, *3*, 821–828. doi:10.1038/nchem.1123.
56. Knupp C, Squire JM. Molecular Packing in Network-Forming Collagens. *Sci. World J.* **2003**, *3*, 558–577. doi:10.1100/tsw.2003.40.
57. Fidler AL, Boudko SP, Rokas A, Hudson BG. The Triple Helix of Collagens—an Ancient Protein Structure That Enabled Animal Multicellularity and Tissue Evolution. *J. Cell Sci.* **2018**, *131*, jcs203950. doi:10.1242/jcs.203950.
58. Kadler KE, Hojima Y, Prockop DJ. Assembly of Collagen Fibrils de Novo by Cleavage of the Type I pC-Collagen with Procollagen C-Proteinase. Assay of Critical Concentration Demonstrates That Collagen Self-Assembly Is a Classical Example of an Entropy-Driven Process. *J. Biol. Chem.* **1987**, *262*, 15696–15701. doi:10.1016/S0021-9258(18)47783-6.
59. Cummings CF, Pedchenko V, Brown KL, Colon S, Rafi M, Jones-Paris C, et al. Extracellular Chloride Signals Collagen IV

- Network Assembly during Basement Membrane Formation. *J. Cell Biol.* **2016**, *213*, 479–494. doi:10.1083/jcb.201510065.
60. Bella J. A First Census of Collagen Interruptions: Collagen's Own Stutters and Stammers. *J. Struct. Biol.* **2014**, *186*, 438–450. doi:10.1016/j.jsb.2014.03.022.
 61. Yurchenco PD, Ruben GC. Basement Membrane Structure in Situ: Evidence for Lateral Associations in the Type IV Collagen Network. *J. Cell Biol.* **1987**, *105*, 2559–2568. doi:10.1083/jcb.105.6.2559.
 62. Elango J, Hou C, Bao B, Wang S, Maté Sánchez De Val JE, Wenhui W. The Molecular Interaction of Collagen with Cell Receptors for Biological Function. *Polymers* **2022**, *14*, 876. doi:10.3390/polym14050876.
 63. Hu K, Hu M, Xiao Y, Cui Y, Yan J, Yang G, et al. Preparation Recombination Human-like Collagen/Fibroin Scaffold and Promoting the Cell Compatibility with Osteoblasts. *J. Biomed. Mater. Res. A* **2021**, *109*, 346–353. doi:10.1002/jbm.a.37027.
 64. Lowell CA, Mayadas TN. Overview: Studying Integrins In Vivo. In *Integrin and Cell Adhesion Molecules*; Shimaoka M, Ed.; Methods in Molecular Biology; Humana Press: Totowa, NJ, USA, 2011; Volume 757, pp. 369–397. doi:10.1007/978-1-61779-166-6_22.
 65. Velling T, Kusche-Gullberg M, Sejersen T, Gullberg D. cDNA Cloning and Chromosomal Localization of Human A11 Integrin. *J. Biol. Chem.* **1999**, *274*, 25735–25742. doi:10.1074/jbc.274.36.25735.
 66. Briesewitz R, Epstein MR, Marcantonio EE. Expression of Native and Truncated Forms of the Human Integrin Alpha 1 Subunit. *J. Biol. Chem.* **1993**, *268*, 2989–2996. doi:10.1016/S0021-9258(18)53871-0.
 67. Iwamoto DV, Calderwood DA. Regulation of Integrin-Mediated Adhesions. *Curr. Opin. Cell Biol.* **2015**, *36*, 41–47. doi:10.1016/j.ceb.2015.06.009.
 68. Shrivastava A, Radziejewski C, Campbell E, Kovac L, McGlynn M, Ryan TE, et al. An Orphan Receptor Tyrosine Kinase Family Whose Members Serve as Nonintegrin Collagen Receptors. *Mol. Cell* **1997**, *1*, 25–34. doi:10.1016/S1097-2765(00)80004-0.
 69. Löffek S, Hurskainen T, Jackow J, Sigloch FC, Schilling O, Tasanen K, et al. Transmembrane Collagen XVII Modulates Integrin Dependent Keratinocyte Migration via PI3K/Rac1 Signaling. *PLoS ONE* **2014**, *9*, e87263. doi:10.1371/journal.pone.0087263.
 70. Yang S, Kim J, Ryu J-H, Oh H, Chun C-H, Kim BJ, et al. Hypoxia-Inducible Factor-2 α Is a Catabolic Regulator of Osteoarthritic Cartilage Destruction. *Nat. Med.* **2010**, *16*, 687–693. doi:10.1038/nm.2153.
 71. Gonzalez DM, Medici D. Signaling Mechanisms of the Epithelial-Mesenchymal Transition. *Sci. Signal.* **2014**, *7*, re8. doi:10.1126/scisignal.2005189.
 72. Ozaki I, Hamajima H, Matsushashi S, Mizuta T. Regulation of TGF- β 1-Induced Pro-Apoptotic Signaling by Growth Factor Receptors and Extracellular Matrix Receptor Integrins in the Liver. *Front. Physiol.* **2011**, *2*, 78. doi:10.3389/fphys.2011.00078.
 73. Madamanchi A, Santoro SA, Zutter MM. α 2 β 1 Integrin. *Adv Exp Med Biol.* **2014**, *819*, 41–60. doi:10.1007/978-94-017-9153-3_3.
 74. Calderwood DA, Tuckwell DS, Eble J, Kühn K, Humphries MJ. The Integrin A1 A-Domain Is a Ligand Binding Site for Collagens and Laminin. *J. Biol. Chem.* **1997**, *272*, 12311–12317. doi:10.1074/jbc.272.19.12311.
 75. Nykvist P, Tu H, Ivaska J, Kämpylä J, Pihlajaniemi T, Heino J. Distinct Recognition of Collagen Subtypes by A1 β 1 and α 2 β 1 Integrins. *J. Biol. Chem.* **2000**, *275*, 8255–8261. doi:10.1074/jbc.275.11.8255.
 76. Kern A, Eble J, Golbik R, Kühn K. Interaction of Type IV Collagen with the Isolated Integrins A1 β 1 and A2 β 1. *Eur. J. Biochem.* **1993**, *215*, 151–159. doi:10.1111/j.1432-1033.1993.tb18017.x.
 77. Jokinen J, Dadu E, Nykvist P, Kämpylä J, White DJ, Ivaska J, et al. Integrin-Mediated Cell Adhesion to Type I Collagen Fibrils. *J. Biol. Chem.* **2004**, *279*, 31956–31963. doi:10.1074/jbc.M401409200.
 78. Kämpylä J, Jääliñoja J, Tulla M, Ylöstalo J, Nissinen L, Viitasalo T, et al. The Fibril-Associated Collagen IX Provides a Novel Mechanism for Cell Adhesion to Cartilaginous Matrix. *J. Biol. Chem.* **2004**, *279*, 51677–51687. doi:10.1074/jbc.M409412200.
 79. Koivunen J, Tu H, Kemppainen A, Anbazhagan P, Finnälä MA, Saarakkala S, et al. Integrin A11 β 1 Is a Receptor for Collagen XIII. *Cell Tissue Res.* **2021**, *383*, 1135–1153. doi:10.1007/s00441-020-03300-y.
 80. Zhang W-M, Kämpylä J, Puranen JS, Knight CG, Tiger C-F, Pentikäinen OT, et al. A11 β 1 Integrin Recognizes the GFOGER Sequence in Interstitial Collagens. *J. Biol. Chem.* **2003**, *278*, 7270–7277. doi:10.1074/jbc.M210313200.
 81. Orgel JPRO, Madhurapantula RS. A Structural Prospective for Collagen Receptors Such as DDR and Their Binding of the Collagen Fibril. *Biochim. Biophys. Acta BBA—Mol. Cell Res.* **2019**, *1866*, 118478. doi:10.1016/j.bbamer.2019.04.008.
 82. Jung SM, Takemura Y, Imamura Y, Hayashi T, Adachi E, Moroi M. Collagen-Type Specificity of Glycoprotein VI as a Determinant of Platelet Adhesion. *Platelets* **2008**, *19*, 32–42. doi:10.1080/09537100701609027.
 83. Schultz HS, Guo L, Keller P, Fleetwood AJ, Sun M, Guo W, et al. OSCAR-collagen Signaling in Monocytes Plays a Proinflammatory Role and May Contribute to the Pathogenesis of Rheumatoid Arthritis. *Eur. J. Immunol.* **2016**, *46*, 952–963. doi:10.1002/eji.201545986.
 84. Son M. Understanding the Contextual Functions of C1q and LAIR-1 and Their Applications. *Exp. Mol. Med.* **2022**, *54*, 567–572. doi:10.1038/s12276-022-00774-4.
 85. Steffensen B, Xu X, Martin PA, Zardeneta G. Human Fibronectin and MMP-2 Collagen Binding Domains Compete for

- Collagen Binding Sites and Modify Cellular Activation of MMP-2. *Matrix Biol.* **2002**, *21*, 399–414. doi:10.1016/S0945-053X(02)00032-X.
86. Sano K, Asanuma-Date K, Arisaka F, Hattori S, Ogawa H. Changes in Glycosylation of Vitronectin Modulate Multimerization and Collagen Binding during Liver Regeneration. *Glycobiology* **2007**, *17*, 784–794. doi:10.1093/glycob/cwm031.
87. Melander MC, Jürgensen HJ, Madsen DH, Engelholm LH, Behrendt N. The Collagen Receptor α PARAP/Endo180 in Tissue Degradation and Cancer (Review). *Int. J. Oncol.* **2015**, *47*, 1177–1188. doi:10.3892/ijo.2015.3120.
88. Chattopadhyay S, Raines RT. Collagen-based Biomaterials for Wound Healing. *Biopolymers* **2014**, *101*, 821–833. doi:10.1002/bip.22486.
89. Huang X, Lv J, Li Y, Mao S, Li Z, Jing Z, et al. Programmable C-to-U RNA Editing Using the Human APOBEC 3A Deaminase. *EMBO J.* **2020**, *39*, e104741. doi:10.15252/embj.2020104741.
90. Sorushanova A, Delgado LM, Wu Z, Shologu N, Kshirsagar A, Raghunath R, et al. The Collagen Suprafamily: From Biosynthesis to Advanced Biomaterial Development. *Adv. Mater.* **2019**, *31*, 1801651. doi:10.1002/adma.201801651.
91. Parenteau-Bareil R, Gauvin R, Berthod F. Collagen-Based Biomaterials for Tissue Engineering Applications. *Materials* **2010**, *3*, 1863–1887. doi:10.3390/ma3031863.
92. Silvipriya K, Kumar K, Bhat A, Kumar B, John A, Lakshmanan P. Collagen: Animal Sources and Biomedical Application. *J. Appl. Pharm. Sci.* **2015**, 123–127. doi:10.7324/JAPS.2015.50322.
93. Fan J, Zhuang Y, Li B. Effects of Collagen and Collagen Hydrolysate from Jellyfish Umbrella on Histological and Immunity Changes of Mice Photoaging. *Nutrients* **2013**, *5*, 223–233. doi:10.3390/nu5010223.
94. Gelse K. Collagens—Structure, Function, and Biosynthesis. *Adv. Drug Deliv. Rev.* **2003**, *55*, 1531–1546. doi:10.1016/j.addr.2003.08.002.
95. Lima CA, Campos JF, Filho JLL, Converti A, Da Cunha MGC, Porto ALF. Antimicrobial and Radical Scavenging Properties of Bovine Collagen Hydrolysates Produced by *Penicillium Aurantiogriseum* URM 4622 Collagenase. *J. Food Sci. Technol.* **2015**, *52*, 4459–4466. doi:10.1007/s13197-014-1463-y.
96. Zhang Y, Olsen K, Grossi A, Otte J. Effect of Pretreatment on Enzymatic Hydrolysis of Bovine Collagen and Formation of ACE-Inhibitory Peptides. *Food Chem.* **2013**, *141*, 2343–2354. doi:10.1016/j.foodchem.2013.05.058.
97. Choi D, Min S-G, Jo Y-J. Functionality of Porcine Skin Hydrolysates Produced by Hydrothermal Processing for Liposomal Delivery System. *J. Food Biochem.* **2018**, *42*, e12464. doi:10.1111/jfbc.12464.
98. Dandagi GL, Byahatti SM. An Insight into the Swine-Influenza A (H1N1) Virus Infection. *Lung India* **2011**, *28*, 34–38.
99. León-López A, Morales-Peñaloza A, Martínez-Juárez VM, Vargas-Torres A, Zeugolis DI, Aguirre-Álvarez G. Hydrolyzed Collagen—Sources and Applications. *Molecules* **2019**, *24*, 4031. doi:10.3390/molecules24224031.
100. Gómez-Guillén MC, Giménez B, López-Caballero ME, Montero MP. Functional and Bioactive Properties of Collagen and Gelatin from Alternative Sources: A Review. *Food Hydrocoll.* **2011**, *25*, 1813–1827. doi:10.1016/j.foodhyd.2011.02.007.
101. Skierka E, Sadowska M. The Influence of Different Acids and Pepsin on the Extractability of Collagen from the Skin of Baltic Cod (*Gadus Morhua*). *Food Chem.* **2007**, *105*, 1302–1306. doi:10.1016/j.foodchem.2007.04.030.
102. Ketnawa S, Benjakul S, Martínez-Alvarez O, Rawdkuen S. Fish Skin Gelatin Hydrolysates Produced by Visceral Peptidase and Bovine Trypsin: Bioactivity and Stability. *Food Chem.* **2017**, *215*, 383–390. doi:10.1016/j.foodchem.2016.07.145.
103. Hong H, Chaplot S, Chalamaiah M, Roy BC, Bruce HL, Wu J. Removing Cross-Linked Teloptides Enhances the Production of Low-Molecular-Weight Collagen Peptides from Spent Hens. *J. Agric. Food Chem.* **2017**, *65*, 7491–7499. doi:10.1021/acs.jafc.7b02319.
104. Hulgán SAH, Hartgerink JD. Recent Advances in Collagen Mimetic Peptide Structure and Design. *Biomacromolecules* **2022**, *23*, 1475–1489. doi:10.1021/acs.biomac.2c00028.
105. Mukherjee S, Varshashankari V, Feba A, Ayyadurai N, Balamurugan K, Shanmugam G. Hyperstable and Fibril-Forming Collagen-Mimetic Peptides in Shortest Triple Helices: Empowering the Capping by π -Systems. *Biomacromolecules* **2025**, *26*, 2171–2185. doi:10.1021/acs.biomac.4c01455.
106. Bourgot I, Primac I, Louis T, Noël A, Maquoi E. Reciprocal Interplay Between Fibrillar Collagens and Collagen-Binding Integrins: Implications in Cancer Progression and Metastasis. *Front. Oncol.* **2020**, *10*, 1488. doi:10.3389/fonc.2020.01488.
107. Mhanna R, Öztürk E, Vallmajo-Martin Q, Millan C, Müller M, Zenobi-Wong M. GFOGER-Modified MMP-Sensitive Polyethylene Glycol Hydrogels Induce Chondrogenic Differentiation of Human Mesenchymal Stem Cells. *Tissue Eng. Part A* **2014**, *20*, 1165–1174. doi:10.1089/ten.tea.2013.0519.
108. Zhao C, Xiao Y, Ling S, Pei Y, Ren J. Structure of Collagen. *Methods Mol. Biol.* **2021**, *2347*, 17–25. doi:10.1007/978-1-0716-1574-4_2
109. Zhang C, Fan D, Shang L, Ma X, Luo Y, Xue W, et al. Optimization of Fermentation Process for Human-like Collagen Production of Recombinant *Escherichia Coli* Using Response Surface Methodology. *Chin. J. Chem. Eng.* **2010**, *18*, 137–142. doi:10.1016/s1004-9541(08)60334-1.
110. Tang Y, Yang X, Hang B, Li J, Huang L, Huang F, et al. Efficient Production of Hydroxylated Human-Like Collagen Via the Coexpression of Three Key Genes in *Escherichia Coli* Origami (DE3). *Appl. Biochem. Biotechnol.* **2016**, *178*, 1458–1470.

- doi:10.1007/s12010-015-1959-6.
111. Nokelainen M, Tu H, Vuorela A, Notbohm H, Kivirikko KI, Myllyharju J. High-level Production of Human Type I Collagen in the Yeast *Pichia Pastoris*. *Yeast* **2001**, *18*, 797–806. doi:10.1002/yea.730.
112. Werkmeister JA, Ramshaw JAM. Recombinant Protein Scaffolds for Tissue Engineering. *Biomed. Mater.* **2012**, *7*, 012002. doi:10.1088/1748-6041/7/1/012002.
113. Rutschmann C, Baumann S, Cabalzar J, Luther KB, Hennet T. Recombinant Expression of Hydroxylated Human Collagen in *Escherichia coli*. *Appl. Microbiol. Biotechnol.* **2014**, *98*, 4445–4455. doi:10.1007/s00253-013-5447-z.
114. Ruggiero F, Exposito J-Y, Bournat P, Gruber V, Perret S, Comte J, et al. Triple Helix Assembly and Processing of Human Collagen Produced in Transgenic Tobacco Plants. *FEBS Lett.* **2000**, *469*, 132–136. doi:10.1016/S0014-5793(00)01259-X.
115. Xu X, Gan Q, Clough RC, Pappu KM, Howard JA, Baez JA, et al. Hydroxylation of Recombinant Human Collagen Type I Alpha 1 in Transgenic Maize Co-Expressed with a Recombinant Human Prolyl 4-Hydroxylase. *BMC Biotechnol.* **2011**, *11*, 69. doi:10.1186/1472-6750-11-69.
116. Vuorela A. Assembly of Human Prolyl 4-Hydroxylase and Type III Collagen in the Yeast *Pichia Pastoris*: Formation of a Stable Enzyme Tetramer Requires Coexpression with Collagen and Assembly of a Stable Collagen Requires Coexpression with Prolyl 4-Hydroxylase. *EMBO J.* **1997**, *16*, 6702–6712. doi:10.1093/emboj/16.22.6702.
117. Myllyharju J, Nokelainen M, Vuorela A. Expression of Recombinant Human Type I–III Collagens in the Yeast *Pichia Pastoris*. *Biochem. Soc. Trans.* **2000**, *28*.
118. Toman PD, Chisholm G, McMullin H, Giere LM, Olsen DR, Kovach RJ, et al. Production of Recombinant Human Type I Procollagen Trimers Using a Four-Gene Expression System in the Yeast *Saccharomyces Cerevisiae*. *J. Biol. Chem.* **2000**, *275*, 23303–23309. doi:10.1074/jbc.M002284200.
119. Liu X, Yang Y, Zhang W, Sun Y, Peng F, Jeffrey L, et al. Expression of Recombinant Protein Using *Corynebacterium Glutamicum*: Progress, Challenges and Applications. *Crit. Rev. Biotechnol.* **2016**, *36*, 652–664. doi:10.3109/07388551.2015.1004519.
120. Li X, Xue W, Zhu C, Fan D, Liu Y, Ma X. Novel Hydrogels Based on Carboxyl Pullulan and Collagen Crosslinking with 1, 4-Butanediol Diglycidylether for Use as a Dermal Filler: Initial in Vitro and in Vivo Investigations. *Mater. Sci. Eng. C* **2015**, *57*, 189–196. doi:10.1016/j.msec.2015.07.059.
121. Kumar V, Kumar N, Gangwar AK, Singh H, Singh R. Comparative Histologic and Immunologic Evaluation of 1,4-Butanediol Diglycidyl Ether Crosslinked versus Noncrosslinked Acellular Swim Bladder Matrix for Healing of Full-Thickness Skin Wounds in Rabbits. *J. Surg. Res.* **2015**, *197*, 436–446. doi:10.1016/j.jss.2015.04.080.
122. Pustlausk W, Paul B, Gelinsky M, Bernhardt A. Jellyfish Collagen and Alginate: Combined Marine Materials for Superior Chondrogenesis of hMSC. *Mater. Sci. Eng. C* **2016**, *64*, 190–198. doi:10.1016/j.msec.2016.03.081.
123. Unsöld C, Pappano WN, Imamura Y, Steigltz BM, Greenspan DS. Biosynthetic Processing of the Pro- $\alpha 1(V)2\alpha 2(V)$ Collagen Heterotrimer by Bone Morphogenetic Protein-1 and Furin-like Proprotein Convertases. *J. Biol. Chem.* **2002**, *277*, 5596–5602. doi:10.1074/jbc.M110003200.
124. Zhou H, Li W, Pan L, Zhu T, Zhou T, Xiao E, et al. Human Extracellular Matrix (ECM)-like Collagen and Its Bioactivity. *Regen. Biomater.* **2024**, *11*, rbae008. doi:10.1093/rb/rbae008.
125. Jia Y, Han Y, Zhang Y, Li L, Zhang B, Yan X. Multifunctional Type I/II Recombinant Human Collagen Incorporated Sodium Alginate Hydrogel with Sustained Release of Extra Cellular Vehicles for Wound Healing Multimodal Therapy in Diabetic Mice. *Regen. Ther.* **2024**, *27*, 329–341. doi:10.1016/j.reth.2024.03.010.
126. Zhuang Z-M, Wang Y, Chen L, Wu Z-R, Zhang T, Bei H-P, et al. Triple-Molded, Reinforced Arrowhead Microneedle Patch of Dual Human-Derived Matrix for Integrated Management of Diabetic Wounds. *Biomaterials* **2026**, *324*, 123520. doi:10.1016/j.biomaterials.2025.123520.
127. Wang Q, An Q, Wang Y, Yang J, Zhang X, Jiang S, et al. Development and Mechanistic Investigation of Recombinant Type III Humanized Collagen Gel for Mid-Facial Soft Tissue Repair. *Collagen Leather* **2025**, *7*, 14. doi:10.1186/s42825-025-00196-8.
128. Munyemana JC, He H, Fu C, Fan Y, Sun X, Xiao J. Recombinant Collagen-Templated Biomimetic Synthesis of Biocompatible pH-Responsive Porous Calcium Carbonate Nanospheres. *ACS Omega* **2023**, *8*, 30879–30887. doi:10.1021/acsomega.3c01467.
129. Zhang H, Wang J, Wei J, Fu X, Ma J, Chen J. Molecular Engineering of Recombinant Protein Hydrogels: Programmable Design and Biomedical Applications. *Gels* **2025**, *11*, 579. doi:10.3390/gels11080579.
130. Vitale M, Ligorio C, Smith IP, Richardson SM, Hoyland JA, Bella J. Incorporation of Natural and Recombinant Collagen Proteins within Fmoc-Based Self-Assembling Peptide Hydrogels. *Gels* **2022**, *8*, 254. doi:10.3390/gels8050254.
131. Gu J, He Y, He C, Zhang Q, Huang Q, Bai S, et al. Advances in the Structures, Mechanisms and Targeting of Molecular Chaperones. *Signal Transduct. Target. Ther.* **2025**, *10*, 84. doi:10.1038/s41392-025-02166-2.
132. Masuda R, Phyu Thant KP, Kawahara K, Oki H, Kadonosono T, Kobayashi Y, et al. A Yeast Two-Hybrid System to Obtain Triple-Helical Ligands from Combinatorial Random Peptide Libraries. *J. Biol. Chem.* **2024**, *300*, 107794.

- doi:10.1016/j.jbc.2024.107794.
133. Ruggiero F, Koch M. Making Recombinant Extracellular Matrix Proteins. *Methods* **2008**, *45*, 75–85. doi:10.1016/j.ymeth.2008.01.003.
 134. Li H-C, Huang C-C, Chen S-F, Chou M-Y. Assembly of Homotrimeric Type XXI Minicollagen by Coexpression of Prolyl 4-Hydroxylase in Stably Transfected Drosophila Melanogaster S2 Cells. *Biochem. Biophys. Res. Commun.* **2005**, *336*, 375–385. doi:10.1016/j.bbrc.2005.08.018.
 135. Shi C, Wang C, Lu J, Zhong B, Tang J. Protein Sequence and Structure Co-Design with Equivariant Translation. *arXiv* **2023**, arXiv:2210.08761.
 136. Evans R, O'Neill M, Pritzel A, Antropova N, Senior A, Green T, et al. Protein Complex Prediction with AlphaFold-Multimer. *BioRxiv* **2021**. doi:10.1101/2021.10.04.463034.
 137. Elder S, Clune J, Walker J, Gloth P. Suitability of EGCG as a Means of Stabilizing a Porcine Osteochondral Xenograft. *J. Funct. Biomater.* **2017**, *8*, 43. doi:10.3390/jfb8040043.
 138. Pawelec KM, Confalonieri D, Ehlicke F, Van Boxtel HA, Walles H, Kluijtmans SGJM. Osteogenesis and Mineralization of Mesenchymal Stem Cells in Collagen Type I-based Recombinant Peptide Scaffolds. *J. Biomed. Mater. Res. A* **2017**, *105*, 1856–1866. doi:10.1002/jbm.a.36049.
 139. Lee JC, Pereira CT, Ren X, Huang W, Bischoff D, Weisgerber DW, et al. Optimizing Collagen Scaffolds for Bone Engineering: Effects of Cross-Linking and Mineral Content on Structural Contraction and Osteogenesis. *J. Craniofac. Surg.* **2015**, *26*, 1992–1996. doi:10.1097/SCS.0000000000001918.
 140. Berndt M, Li Y, Seyedhassantehrani N, Yao L. Fabrication and Characterization of Microspheres Encapsulating Astrocytes for Neural Regeneration. *ACS Biomater. Sci. Eng.* **2017**, *3*, 1313–1321. doi:10.1021/acsbiomaterials.6b00229.
 141. Han L, Zhang Z, Wang B, Wen Z. Construction and Biocompatibility of a Thin Type I/II Collagen Composite Scaffold. *Cell Tissue Bank.* **2018**, *19*, 47–59. doi:10.1007/s10561-017-9653-2.
 142. Wang X, Ma B, Chang J. Preparation of Decellularized Vascular Matrix by Co-Crosslinking of Procyanidins and Glutaraldehyde. *Biomed. Mater. Eng.* **2015**, *26*, 19–30. doi:10.3233/BME-151548.
 143. Wang X, Xu K, Ma L, Sun R, Wang K, Wang R, et al. Diffusion Model Assisted Designing Self-Assembling Collagen Mimetic Peptides as Biocompatible Materials. *Brief. Bioinform.* **2024**, *26*, bbae622. doi:10.1093/bib/bbae622.
 144. Khare E, Yu C-H, Gonzalez Obeso C, Milazzo M, Kaplan DL, Buehler MJ. Discovering Design Principles of Collagen Molecular Stability Using a Genetic Algorithm, Deep Learning, and Experimental Validation. *Proc. Natl. Acad. Sci. USA* **2022**, *119*, e2209524119. doi:10.1073/pnas.2209524119.
 145. Hu J, Li J, Jiang J, Wang L, Roth J, McGuinness KN, et al. Design of Synthetic Collagens That Assemble into Supramolecular Banded Fibers as a Functional Biomaterial Testbed. *Nat. Commun.* **2022**, *13*, 6761. doi:10.1038/s41467-022-34127-6.
 146. Köster S, Evans HM, Wong JY, Pfohl T. An In Situ Study of Collagen Self-Assembly Processes. *Biomacromolecules* **2008**, *9*, 199–207. doi:10.1021/bm700973t.
 147. Hafner AE, Gyori NG, Bench CA, Davis LK, Šarić A. Modeling Fibrillogenesis of Collagen-Mimetic Molecules. *Biophys. J.* **2020**, *119*, 1791–1799. doi:10.1016/j.bpj.2020.09.013.
 148. Li Z, Du T, Ruan C, Niu X. Bioinspired Mineralized Collagen Scaffolds for Bone Tissue Engineering. *Bioact. Mater.* **2021**, *6*, 1491–1511. doi:10.1016/j.bioactmat.2020.11.004.
 149. Shen H, Fallas JA, Lynch E, Sheffler W, Parry B, Jannetty N, et al. De Novo Design of Self-Assembling Helical Protein Filaments. *Science* **2018**, *362*, 705–709. doi:10.1126/science.aau3775.
 150. LeCun Y, Bengio Y, Hinton G. Deep Learning. *Nature* **2015**, *521*, 436–444. doi:10.1038/nature14539.
 151. Srinivasan A, Gupta A, Narayanamurthy V. A Comprehensive Review of AI-Based Collagen Valorization: Recent Trends, Innovations in Extraction, and Applications. *Green Anal. Chem.* **2025**, *12*, 100212. doi:10.1016/j.greeac.2025.100212.
 152. Li W, Peng J, Yao D, Rao B, Xia Y, Wang Q, et al. The Structural Basis for the Collagen Processing by Human P3H1/CRTAP/PPIB Ternary Complex. *Nat. Commun.* **2024**, *15*, 7844. doi:10.1038/s41467-024-52321-6.
 153. Qian Y, Xu C, Xiong W, Jiang N, Zheng Y, He X, et al. Dual Cross-Linked Organic-Inorganic Hybrid Hydrogels Accelerate Diabetic Skin Wound Healing. *Chem. Eng. J.* **2021**, *417*, 129335. doi:10.1016/j.cej.2021.129335.
 154. Yao T, Chen H, Wang R, Rivero R, Wang F, Kessels L, et al. Thiol-Ene Conjugation of a VEGF Peptide to Electrospun Scaffolds for Potential Applications in Angiogenesis. *Bioact. Mater.* **2023**, *20*, 306–317. doi:10.1016/j.bioactmat.2022.05.029.
 155. Conde J, Oliva N, Atilano M, Song HS, Artzi N. Self-Assembled RNA-Triple-Helix Hydrogel Scaffold for microRNA Modulation in the Tumour Microenvironment. *Nat. Mater.* **2016**, *15*, 353–363. doi:10.1038/nmat4497.
 156. Kubyshevskiy V. Stabilization of the Triple Helix in Collagen Mimicking Peptides. *Org. Biomol. Chem.* **2019**, *17*, 8031–8047. doi:10.1039/C9OB01646E.
 157. Lyu C, Kong W, Liu Z, Wang S, Zhao P, Liang K, et al. Advanced Glycation End-Products as Mediators of the Aberrant Crosslinking of Extracellular Matrix in Scarred Liver Tissue. *Nat. Biomed. Eng.* **2023**, *7*, 1437–1454. doi:10.1038/s41551-023-01019-z.
 158. Wang J, Wu Q, Wang Y, Xiang L, Feng J, Zhou Z, et al. Collagenase-Loaded pH-Sensitive Nanocarriers Efficiently Remodeled

- Tumor Stroma Matrixes and Improved the Enrichment of Nanomedicines. *Nanoscale* **2021**, *13*, 9402–9414. doi:10.1039/D1NR00950H.
159. Le DHT, Ibrahimova V, Van Den Wildenberg SAH, Wu H, Fonseca A, Torres T, et al. Light-Responsive Elastin-Like Peptide-Based Targeted Nanoparticles for Enhanced Spheroid Penetration. *Angew. Chem. Int. Ed.* **2023**, *62*, e202300511. doi:10.1002/anie.202300511.
 160. Li Y, Xia Y, Liu X, Wang J, Sun Y, Huang J, et al. Rational Design of Bioengineered Recombinant Collagen-like Protein Enhances GelMA Hydrogel for Diabetic Wound Healing. *Int. J. Biol. Macromol.* **2024**, *280*, 136012. doi:10.1016/j.ijbiomac.2024.136012.
 161. Sun TL, Luo F, Kurokawa T, Karobi SN, Nakajima T, Gong JP. Molecular Structure of Self-Healing Polyampholyte Hydrogels Analyzed from Tensile Behaviors. *Soft Matter* **2015**, *11*, 9355–9366. doi:10.1039/C5SM01423A.
 162. Yu HC, Zheng SY, Fang L, Ying Z, Du M, Wang J, et al. Reversibly Transforming a Highly Swollen Polyelectrolyte Hydrogel to an Extremely Tough One and Its Application as a Tubular Grasper. *Adv. Mater.* **2020**, *32*, 2005171. doi:10.1002/adma.202005171.
 163. Meyers MA, McKittrick J, Chen P-Y. Structural Biological Materials: Critical Mechanics-Materials Connections. *Science* **2013**, *339*, 773–779. doi:10.1126/science.1220854.
 164. Su R, Ma C, Han B, Zhang H, Liu K. Proteins for Hyperelastic Materials. *Small* **2025**, *21*, 2406388. doi:10.1002/smll.202406388.
 165. Mozdzen LC, Rodgers R, Banks JM, Bailey RC, Harley BAC. Increasing the Strength and Bioactivity of Collagen Scaffolds Using Customizable Arrays of 3D-Printed Polymer Fibers. *Acta Biomater.* **2016**, *33*, 25–33. doi:10.1016/j.actbio.2016.02.004.
 166. Hadidi P, Cissell DD, Hu JC, Athanasiou KA. Temporal Development of Near-Native Functional Properties and Correlations with qMRI in Self-Assembling Fibrocartilage Treated with Exogenous Lysyl Oxidase Homolog 2. *Acta Biomater.* **2017**, *64*, 29–40. doi:10.1016/j.actbio.2017.09.035.
 167. Priyadarshani P, Li Y, Yang S, Yao L. Injectable Hydrogel Provides Growth-permissive Environment for Human Nucleus Pulposus Cells. *J. Biomed. Mater. Res. A* **2016**, *104*, 419–426. doi:10.1002/jbm.a.35580.
 168. Zhou X, Wang J, Fang W, Tao Y, Zhao T, Xia K, et al. Genipin Cross-Linked Type II Collagen/Chondroitin Sulfate Composite Hydrogel-like Cell Delivery System Induces Differentiation of Adipose-Derived Stem Cells and Regenerates Degenerated Nucleus Pulposus. *Acta Biomater.* **2018**, *71*, 496–509. doi:10.1016/j.actbio.2018.03.019.
 169. Bryś M, Urbańska K, Olas B. Novel Findings Regarding the Bioactivity of the Natural Blue Pigment Genipin in Human Diseases. *Int. J. Mol. Sci.* **2022**, *23*, 902.
 170. Vardar E, Larsson HM, Allazetta S, Engelhardt EM, Pinnagoda K, Vythilingam G, et al. Microfluidic Production of Bioactive Fibrin Micro-Beads Embedded in Crosslinked Collagen Used as an Injectable Bulking Agent for Urinary Incontinence Treatment. *Acta Biomater.* **2018**, *67*, 156–166. doi:10.1016/j.actbio.2017.11.034.
 171. Quinlan E, Thompson EM, Matsiko A, O'Brien FJ, López-Noriega A. Functionalization of a Collagen-Hydroxyapatite Scaffold with Osteostatin to Facilitate Enhanced Bone Regeneration. *Adv. Healthc. Mater.* **2015**, *4*, 2649–2656. doi:10.1002/adhm.201500439.
 172. Liu T, Dan W, Dan N, Liu X, Liu X, Peng X. A Novel Grapheme Oxide-Modified Collagen-Chitosan Bio-Film for Controlled Growth Factor Release in Wound Healing Applications. *Mater. Sci. Eng. C* **2017**, *77*, 202–211. doi:10.1016/j.msec.2017.03.256.
 173. Baird CW, Myers PO, Piekarski B, Borisuk M, Majeed A, Emani SM, et al. Photo-Oxidized Bovine Pericardium in Congenital Cardiac Surgery: Single-Centre Experience. *Interact. Cardiovasc. Thorac. Surg.* **2016**, *24*, 240–244. doi:10.1093/icvts/ivw315.
 174. Rosellini E, Zhang YS, Migliori B, Barbani N, Lazzeri L, Shin SR, et al. Protein/Polysaccharide-based Scaffolds Mimicking Native Extracellular Matrix for Cardiac Tissue Engineering Applications. *J. Biomed. Mater. Res. A* **2018**, *106*, 769–781. doi:10.1002/jbm.a.36272.
 175. Chen C, Zhao M, Zhang R, Lu G, Zhao C, Fu F, et al. Collagen/Heparin Sulfate Scaffolds Fabricated by a 3D Bioprinter Improved Mechanical Properties and Neurological Function after Spinal Cord Injury in Rats. *J. Biomed. Mater. Res. A* **2017**, *105*, 1324–1332. doi:10.1002/jbm.a.36011.
 176. Siriwardane ML, DeRosa K, Collins G, Pfister BJ. Controlled Formation of Cross-Linked Collagen Fibers for Neural Tissue Engineering Applications. *Biofabrication* **2014**, *6*, 015012. doi:10.1088/1758-5082/6/1/015012.
 177. Li Y, He Q, Hu X, Liu Y, Cheng X, Li X, et al. Improved Performance of Collagen Scaffolds Crosslinked by Traut's Reagent and Sulfo-SMCC. *J. Biomater. Sci. Polym. Ed.* **2017**, *28*, 629–647. doi:10.1080/09205063.2017.1291296.
 178. Bell A, Kofron M, Nistor V. Multiphoton Crosslinking for Biocompatible 3D Printing of Type I Collagen. *Biofabrication* **2015**, *7*, 035007. doi:10.1088/1758-5090/7/3/035007.
 179. Fadlallah A, Zhu H, Arafat S, Kochevar I, Melki S, Ciolino JB. Corneal Resistance to Keratolysis After Collagen Crosslinking with Rose Bengal and Green Light. *Investig. Ophthalmology Vis. Sci.* **2016**, *57*, 6610. doi:10.1167/iovs.15-18764.
 180. Moreira MA, Souza NO, Sousa RS, Freitas DQ, Lemos MV, De Paula DM, et al. Efficacy of New Natural Biomodification Agents from Anacardiaceae Extracts on Dentin Collagen Cross-Linking. *Dent. Mater.* **2017**, *33*, 1103–1109.

doi:10.1016/j.dental.2017.07.003.

181. Lim E, Lim M-J, Min K-S, Kwon Y-S, Hwang Y-C, Yu M-K, et al. Effects of Epicatechin, a Crosslinking Agent, on Human Dental Pulp Cells Cultured in Collagen Scaffolds. *J. Appl. Oral Sci.* **2016**, 24, 76–84. doi:10.1590/1678-775720150383.